arXiv:cond-mat/0111041v1 [cond-mat.supr-con] 2 Nov 2001

# Evidence for Linelike Vortex Liquid Phase in $Tl_2Ba_2CaCu_2O_8$ Probed by the Josephson Plasma Resonance

V. K. Thorsmølle[1], R. D. Averitt[1], M. P. Maley[1], M. F. Hundley[1], A. E. Koshelev[2], L. N. Bulaevskii[1], and A. J. Taylor[1]
[1]*Los Alamos National Laboratory, Los Alamos, NM 87545*
[2]*Materials Science Division, Argonne National Laboratory, Argonne, IL 60469*

(February 1, 2008)

We measured the Josephson plasma resonance (JPR) in optimally doped $Tl_2Ba_2CaCu_2O_{8+\delta}$ thin films using terahertz time-domain spectroscopy in transmission. The temperature and magnetic field dependence of the JPR frequency shows that the $c$-axis correlations of pancake vortices remain intact at the transition from the vortex solid to the liquid phase. In this respect $Tl_2Ba_2CaCu_2O_{8+\delta}$ films, with anisotropy parameter $\gamma \approx 150$, are similar to the less anisotropic $YBa_2Cu_3O_{7-\delta}$ ($\gamma \approx 8$) rather than to the most anisotropic $Bi_2Sr_2CaCu_2O_{8+\delta}$ single crystals ($\gamma \geq 500$).

74.60.Ge

The structure of the different vortex phases and the nature of the phase transitions in the magnetic phase diagram of high-$T_c$ superconductors has been the subject of intense study over the past several years [1]. It has been established rather conclusively, both experimentally [2,3] and theoretically, that there exists a first-order phase transition at which the vortex lattice melts into a vortex liquid where at least in-plane long-range order is lost. This melting transition depends strongly on the anisotropy parameter, $\gamma = \lambda_c/\lambda_{ab}$, of the superconductor [4]. Here $\lambda_c$ and $\lambda_{ab}$ are the London penetration depths along the $c$-axis and $ab$-plane, respectively. In $YBa_2Cu_3O_{7-\delta}$ (Y-123), which has a low degree of anisotropy $\gamma \sim 8$, the vortex lattice melts by a first-order phase transition into a linelike liquid [5] up to rather high magnetic fields $\sim 1-10$ T [3]. In the case of strong anisotropy $\gamma \sim 500$ and $\sim 150$ as in, respectively, Bi- and Tl-based high-$T_c$ superconductors a model has been introduced, whereby the vortices are stacks of two-dimensional "pancake" vortices in the $CuO_2$ layers weakly coupled by Josephson and magnetic interactions [7]. At low temperatures and magnetic fields the vortex lattice is composed of aligned stacks of pancakes (vortex lines). However, the interactions between pancakes in adjacent layers are very weak and vortex lines are easily destroyed by either thermal fluctuations at high temperatures, or by random pinning. In $Bi_2Sr_2CaCu_2O_{8+\delta}$ (Bi-2212), which is the most anisotropic superconductor known, the vortex lattice undergoes a first-order melting into a pancake liquid at magnetic fields $B \lesssim 500$ G [4].

The structure of the vortex liquid phase in the anisotropic superconductors Y-123 and Bi-2212 has been the focus of numerous experimental and theoretical studies, e.g. Refs. [5,8,9]. It has been found that at the melting transition in Bi-2212 vortex lines are disintegrated into a liquid of pancakes [8,9], in contrast to Y-123, where vortex lines are preserved above the melting line [5]. In this Letter we report on the structure of the vortex state below and near the glass transition in Tl-2212 films, which have an intermediate anisotropy in between Bi-2212 and Y-123. We show that with respect to $c$-axis correlations in the liquid phase in fields below 0.25 T Tl-2212 films behave as Y-123 with strong disorder [6].

The $c$-axis correlations of pancake vortices are directly related to the interlayer phase coherence in the mixed-state [10]. One of the most powerful experimental probes for the interlayer phase coherence in highly anisotropic layered superconductors is the $c$-axis Josephson plasma resonance [9,11]. The JPR is a Cooper pair charge oscillation mode perpendicular to the $CuO_2$ layers. In zero magnetic field the JPR is a direct probe of the Josephson coupling between the layers [12]. The JPR frequency is given by: $\omega_0(T) = c/[\lambda_c(T)\sqrt{\epsilon_\infty}] = c/[\gamma\lambda_{ab}(T)\sqrt{\epsilon_\infty}]$. Here, $c$ is the speed of light, and $\epsilon_\infty$ is the high-frequency dielectric constant along the $c$-axis. In the presence of a $c$-axis magnetic field $B$, the JPR can be written as [10]

$$\omega_p^2(B,T) = \omega_0^2(T)\langle\cos[\varphi_{n,n+1}(\mathbf{r},B)]\rangle. \tag{1}$$

Here, $\langle\cos[\varphi_{n,n+1}(\mathbf{r},B)]\rangle$ is the local thermal and disorder average of the cosine of the gauge-invariant phase difference between adjacent layers $n$ and $n+1$, and $\mathbf{r}$ is the in-plane coordinate. When the pancake vortices form straight lines perpendicular to the layers, $\varphi_{n,n+1}(\mathbf{r},B)$ vanishes. However, when the pancake vortices are misaligned along the $c$-axis, a nonzero phase difference is induced, which suppresses the interlayer Josephson coupling, and results in the reduction of $\langle\cos\varphi_{n,n+1}\rangle$ from unity. Thus, the JPR probes the correlations of pancake vortices along the $c$-axis, providing information on various phases and phase transitions in the vortex state.

Recent JPR microwave measurements in a Bi-2212 crystal [8,9] show a jump in the interlayer phase coherence factor, $\langle\cos\varphi_{n,n+1}\rangle$, from ≈0.65-0.7 to ≈0.3-0.4 at the first-order melting transition. These data, together with magnetization measurements, show that the melting of the vortex lattice is accompanied by disintegration of vortex lines into a pancake liquid, where $c$-axis correlations are lost. Quantitative analysis [10] of the

JPR data confirmed that correlations of pancakes between neighboring layers in the liquid phase in Bi-2212 far away from $T_c$ are practically absent. Only at very low melting fields, $B_m < B_J = \Phi_0/\lambda_J^2 \approx 20$ G, near $T_c$ does the JPR data [8,9] show evidence of a linelike liquid [13]. Here $\lambda_J = \gamma s$ is the Josephson length where $s$ is the interlayer distance. Vortex lines (stacks of pancake vortices) are preserved across the melting transition when the intervortex distance is much larger than the meandering length, $r_w$, defined as the average in-plane distance between two pancake vortices in adjacent layers belonging to the same vortex line.

To probe $c$-axis correlations in less anisotropic high-$T_c$ superconductors, such as thallium and mercury compounds, where the JPR lies in the THz range, one needs optical techniques. Demonstrated techniques are either grazing incidence reflectivity [14], or terahertz time-domain spectroscopy (THz-TDS) in transmission [11]. Here we report study of the JPR by use of THz-TDS in transmission. THz-TDS has a better signal-to-noise ratio, in comparison to grazing incidence reflectivity, allowing measurements close to $T_c$ [11]. Details of the THz-TDS spectrometer are discussed in Refs. [15,16]. The Tl-2212 film (700 nm) was grown on a 10 × 10 mm$^2$ MgO substrate, and exhibited a sharp transition (0.2 K width) at $T_c = 103.4$ K. The growth process is described in Ref. [11]. The sample was positioned inside a cryostat with optical access, between a pair of permanent magnets with the magnetic field oriented along the $c$-axis. Measurements were performed in field cooled mode. In order to excite the JPR, $p$-polarized THz radiation, incident at an angle of 45° to the surface normal, is transmitted through the sample [11].

Fig. 1 shows the electric field of the THz pulse transmitted through the sample. Fig. 1(a) shows the oscillations due to the JPR in the time-domain at 70 K and 80 K. This clearly illustrates a downward shift in the oscillation frequency as the temperature ($T$) is increased from 70 K to 80 K. Fig. 1(b) shows the JPR in the time-domain at 70 K in zero magnetic field and in a 2.5 kG $c$-axis field. Here we clearly see the distortion of the THz pulse by vortices induced by the magnetic field. It is caused by both diminishing of the oscillation frequency and broadening of the JPR peak due to the disorder in pancake positions.

To obtain the transmission amplitude of the Tl-2212 film, we performed two sets of averaged scans at each temperature and field. The first set was performed on the sample (film plus substrate), and the other set was performed on a bare reference substrate. The fast Fourier transform of the sample was then divided by the fast Fourier transform of the reference. This ratio gave the complex transmission coefficient of the Tl-2212 film as a function of frequency. Fig. 2 shows the transmission amplitude as a function of frequency for the Tl-2212 film (a) in zero field from 70 to 100 K, and (b) in a 2.5 kG field applied along the $c$-axis. The inset in Fig. 2(b) shows the decrease of the JPR frequency with temperature at $B = 0$ and $B = 2.5$ kG, which clearly shows the sensitivity of the JPR to the vortex state.

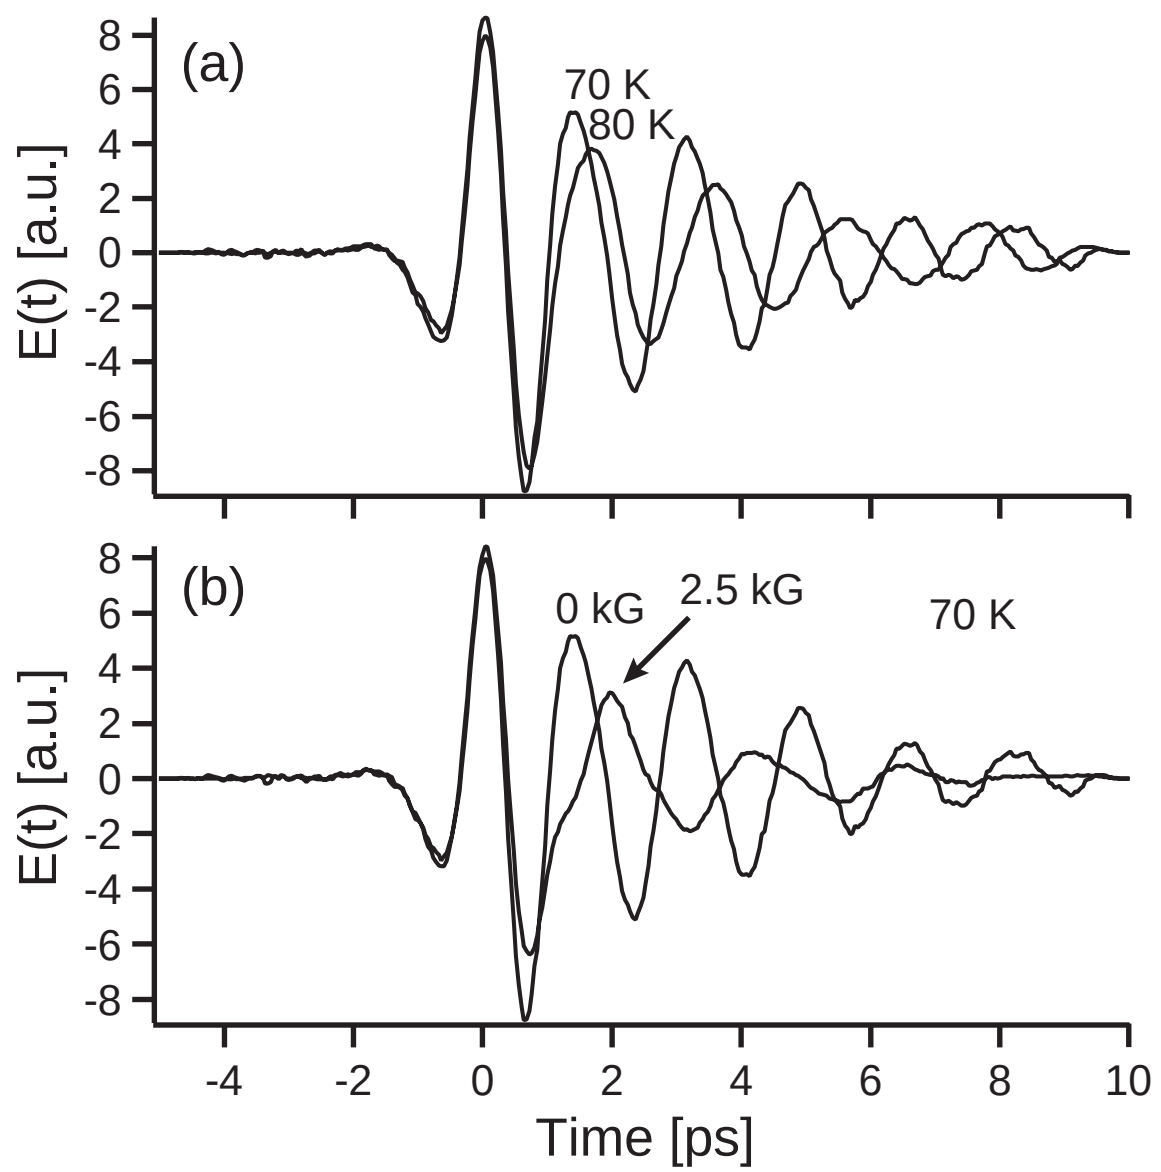

FIG. 1. Electric field of THz pulse in the time-domain transmitted through Tl-2212 thin film at (a) 70 K and 80 K, and at (b) 70 K with and without a 2.5 kG $c$-axis field.

The interlayer phase coherence factor, $\langle\cos\varphi_{n,n+1}\rangle = \omega_p^2\,(B,T)\,/\omega_0^2\,(0,20\,\mathrm{K})$ (determined using data as shown in Fig. 2), as a function of $T$ at different fields is shown in Fig. 3. This factor is practically $T$-independent from 20 to 70 K at $B = 0.4$ kG, and from 20 to 50 K at $B = 1.8$ kG. This suggests that the pancake vortices are well pinned and largely unaffected by thermal fluctuations at lower $T$ in the vortex solid phase. $\langle\cos\varphi_{n,n+1}\rangle$ decreases linearly with field at 20 K $\leq T \leq$ 50 K. Such a field dependence was also observed in the vortex solid phase in Bi-2212 [8,9]. At higher $T$ the drop of $\langle\cos\varphi_{n,n+1}\rangle$ with field becomes stronger, in agreement with theoretical predictions [17]. We note that Dulić *et al.* [20] did not observe a change in the field dependence of the JPR frequency, $\omega_p(B)$, with temperature in grazing incidence reflectivity measurements up to 70 K. The important point is that there is no indication of a sudden change of the field dependence as a function of $T$, which would have signaled a disintegration of vortex lines into a pancake liquid at the melting transition, as observed in Bi-2212 crystals.

For proper interpretation of our data it is important to determine the transition from the liquid to solid phase and the nature of this transition (melting or glass). To address this issue we performed $I-V$ measurements in fields from 0.5 to 1.5 kG as a function of $T$. Fig. 4 shows the scaled $I-V$ curves in 1.0 kG. We determined the glass transition temperature $T_g$ by scaling the nonlinear $I-V$ curves via the Bose-glass model [18]. When scaled, the $I-V$ data fall onto different curves for temperatures

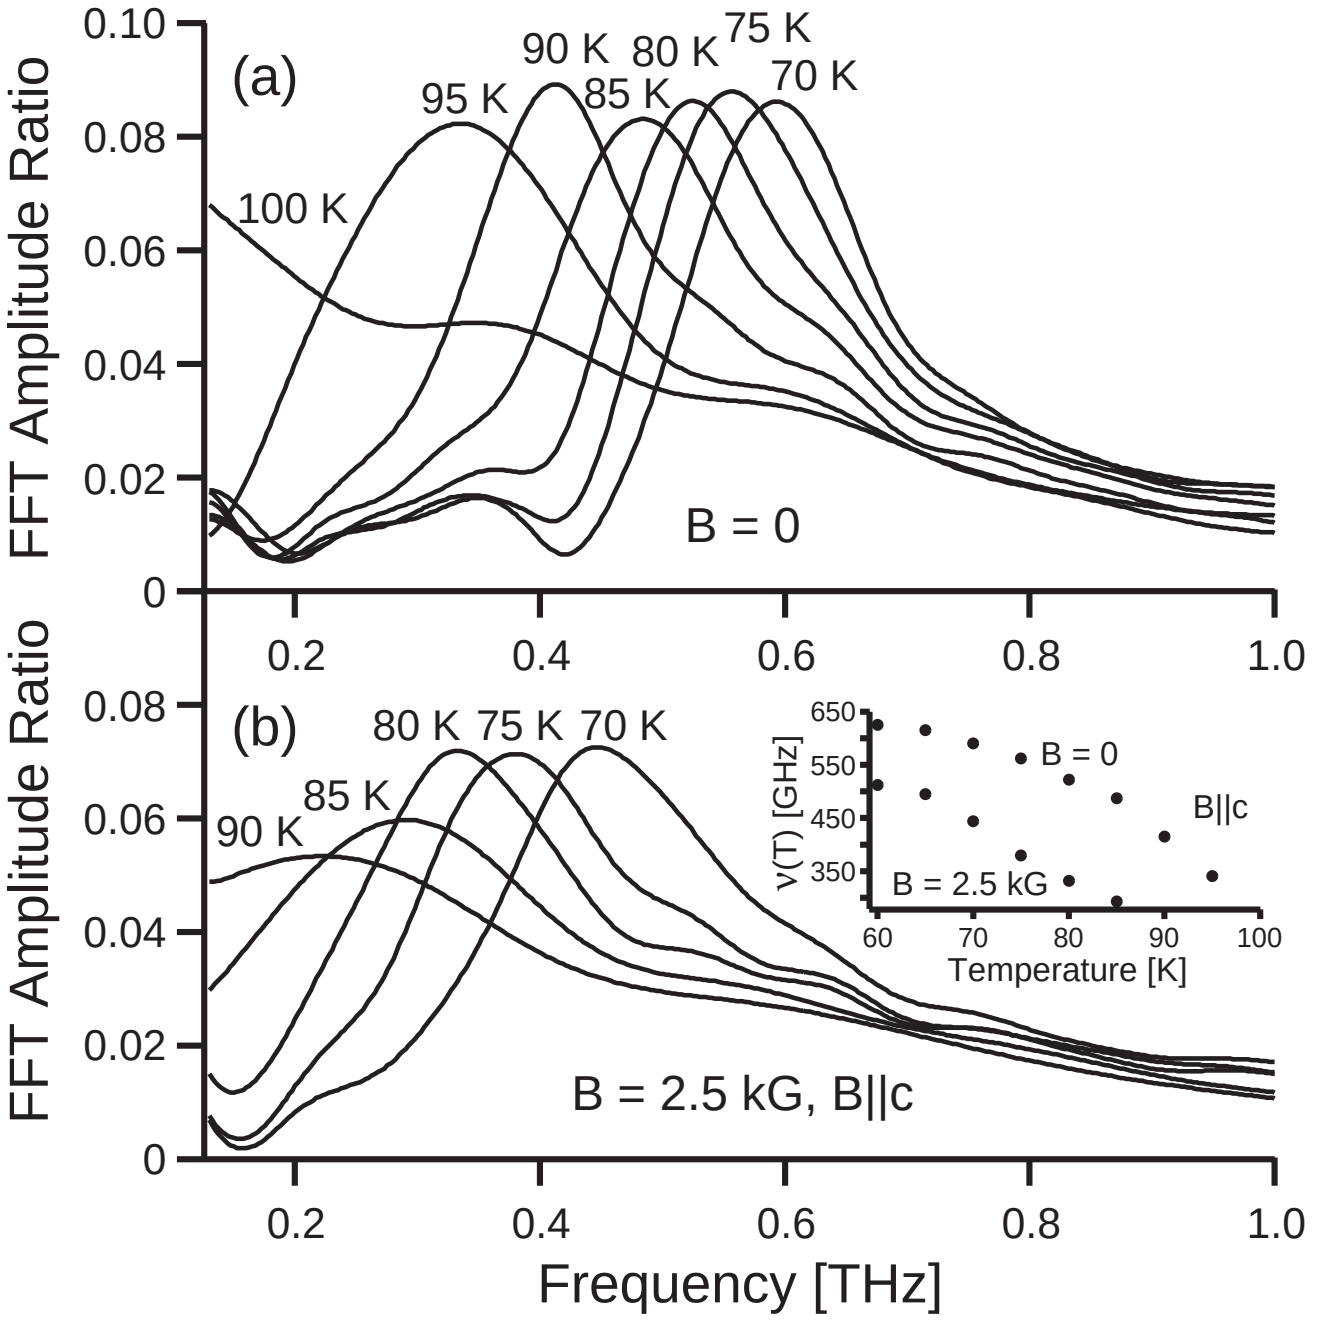

FIG. 2. Transmission amplitude versus frequency for Tl-2212 thin film. (a) JPR in zero field from 70 K to 100 K. (b) JPR in 2.5 kG field applied along the $c$-axis from 70 K to 90 K. The inset shows the JPR frequency versus temperature for $B = 0$ kG, and $B = 2.5$ kG.

above and below $T_g$. The positions of $T_g$ determined in this manner at 70, 75, and 85 K are depicted in Fig. 5. Hence, in our films the melting transition is replaced by the glass transition due to disorder inherent to the films. Paulius *et al* [6] observed such replacement in Y-123 crystals under the effect of controlled disorder introduced by proton irradiation. For Tl-2212 single crystals, the irreversibility line was observed from magnetization measurements by Hardy *et al.* [21] at fields of 0.7, 0.6 and 0.3 kG at $T = 70$, 75 and 85 K, respectively (see Fig. 5). In films the melting or glass transition field is strongly enhanced by pinning as compared to single crystals.

Next we address whether we have linelike vortices in the solid and liquid phases and how these phases differ with respect to $c$-axis correlations. For this we discuss the field dependence of the coherence factor $\langle \cos\varphi_{n,n+1}\rangle$ below and through this transition.

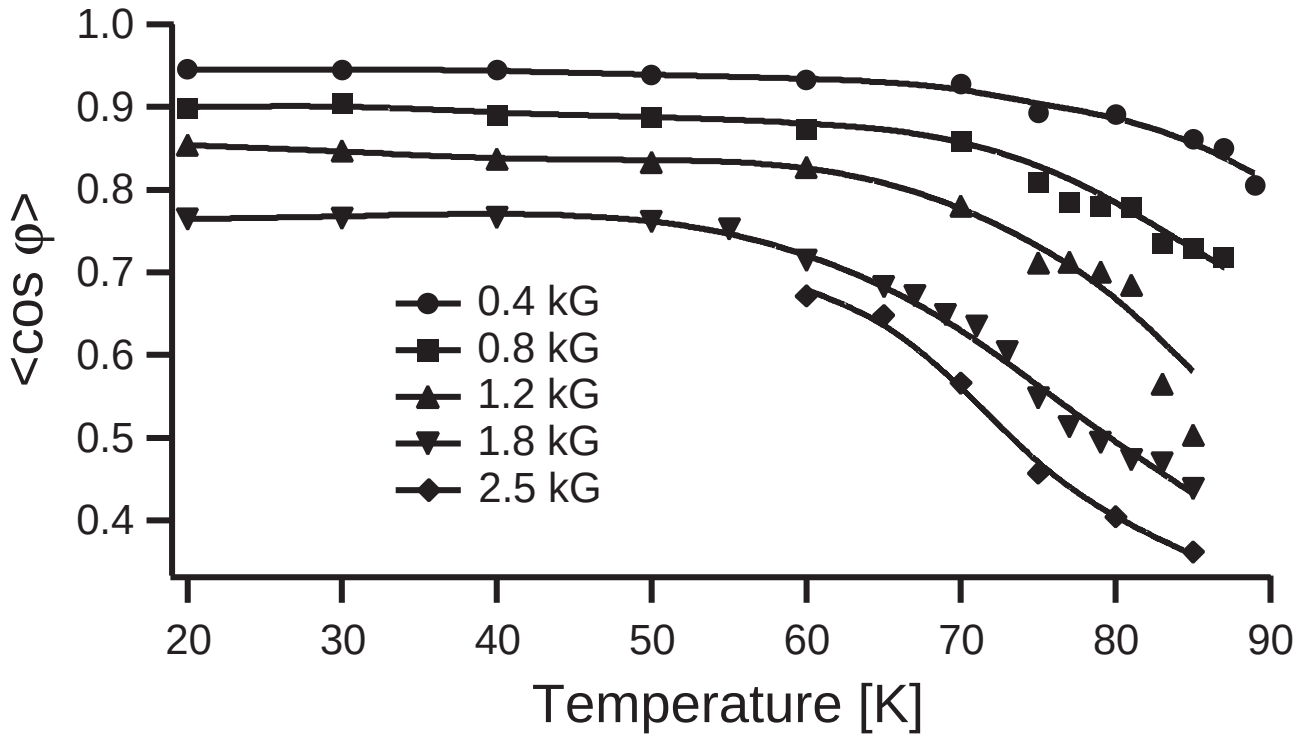

FIG. 3. Interlayer phase coherence factor, $\langle \cos\varphi_{n,n+1}\rangle$, versus temperature in Tl-2212 films at different magnetic fields applied along the $c$-axis.

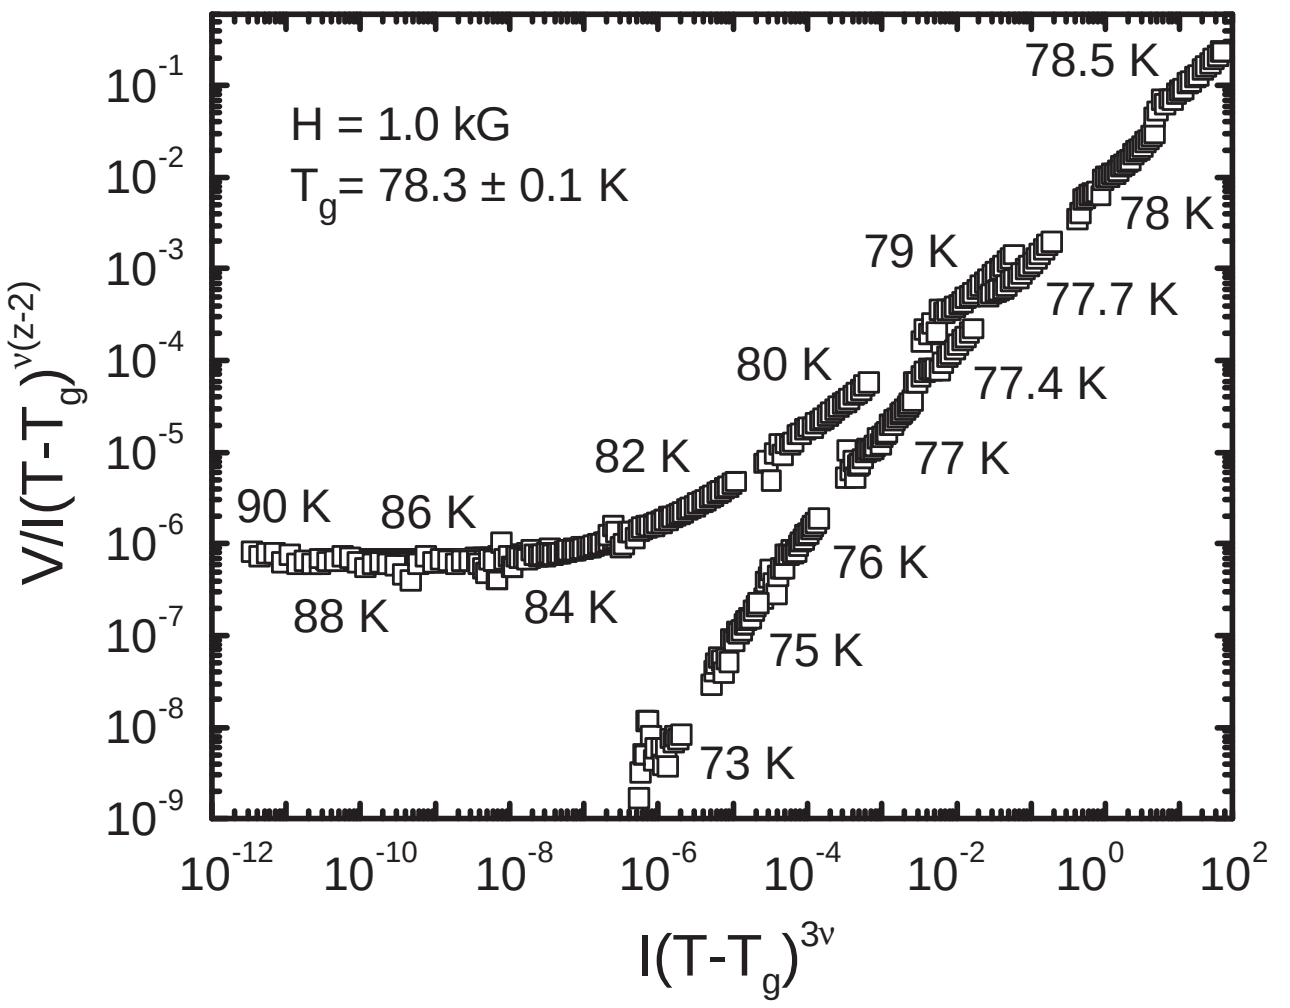

FIG. 4. Scaling of $I-V$ curves following the Bose-glass model procedure [19], measured from 73 to 90 K at 1 kG. We obtain the exponents $\nu = 1.7 \pm 0.1$ and $z = 4.5 \pm 0.2$. At this field we find $T_g = 78.3 \pm 0.1$ K.

Suppression of the Josephson coupling due to pinning-induced meandering of vortex lines at low $T$ has been considered in Ref. [22]. Let us discuss the isolated vortex regime at low fields $B \ll \Phi_0/4\pi\lambda_{ab}^2, B_J$, i.e. well below 0.05 T. Here the coherence factor drops linearly with $B$,

$$\langle \cos\varphi_{n,n+1}\rangle = 1 - \frac{B}{B_w}, \quad B_w \approx \frac{\Phi_0}{\pi r_w^2 \ln(\gamma s/r_w)}, \qquad (2)$$

where the field $B_w$ is a measure of the meandering length $r_w$. $r_w$, in turn, is determined by a balance between the pinning energy $U_p$ and the Josephson energy, $E_J = \Phi_0^2/16\pi^3 s\lambda_c^2$, $r_w^2 \sim U_p/E_J$. Our data, Fig. 3, give $B_w \approx 8$ kG corresponding to $r_w \approx 25$ nm. This value for $B_w$ has to be compared with the lower value $\approx 1.2$ kG for the more anisotropic Bi-2212 [9], the similar value for a different Tl-2212 film, $\approx 14$ kG [20], and with the much higher value $\approx 30$ T for the less anisotropic underdoped Y-123 [20]. This shows that $B_w$ is mainly determined by the anisotropy of the material. In the isolated vortex regime we found an intervortex distance $a = \sqrt{\Phi_0/B} > 200$ nm. Hence, disorder does not destroy vortex lines.

At higher temperatures, meandering of vortex lines is determined by thermal fluctuations. We calculate the $T$- and $B$-dependence of the interlayer phase coherence factor, $\langle \cos\varphi_{n,n+1}\rangle$, in the vortex solid phase neglecting pinning but accounting for Gaussian thermal fluctuations of pancakes [17], accounting for both Josephson and magnetic coupling of the layers. Calculations are based on the Lawrence-Doniach model in the London limit, which is completely defined by the London penetration depths $\lambda_c$ and $\lambda_{ab}$, and the interlayer spacing, $s = 15$ Å. We extract $\lambda_c$ ($\approx 0.003$ cm at 70 K) directly from the JPR frequency using $\epsilon_\infty = 9.1$ [23]. We find

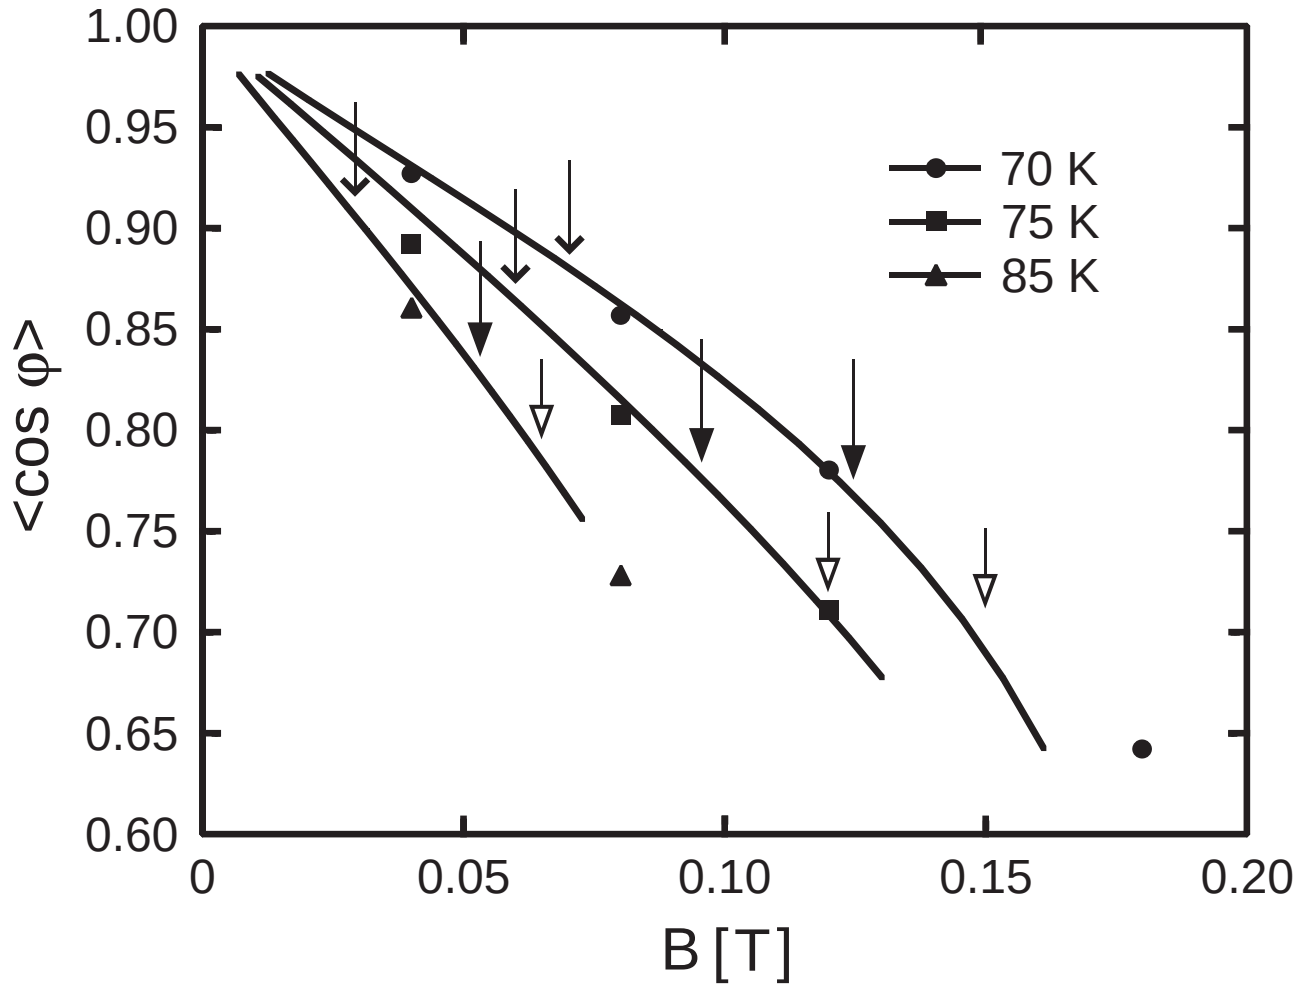

FIG. 5. Comparison between experimental data (symbols) for the interlayer phase coherence factor, $\langle \cos \varphi_{n,n+1} \rangle$, in Tl-2212 films at 70, 75 and 85 K, and numerical calculations (solid lines) based on Ref. [17]. Calculations were done using $\lambda_c$ extracted directly from the JPR frequency with $\epsilon_\infty = 9.1$ and assuming the anisotropy factor $\gamma = 150$. Arrows mark glass transitions determined from transport measurements (open arrows) and estimated melting transition (closed arrows). Simple arrows indicate irreversibility line in single crystals [21].

that the best agreement between calculation and experiment is achieved using $\gamma = 150$, see Fig. 5. This value of $\gamma$ is consistent with the resistivity anisotropy of Tl-2212 single crystals near $T_c$ [21].

Extracted parameters of our film allow us to calculate the *expected* location of the melting transition at different fields for a corresponding clean material. In superconductors with dominating Josephson coupling, $\gamma < \lambda/s$, the melting temperature is given by $T_m \approx 0.13\epsilon_0 a/\gamma$ with $\epsilon_0 = \Phi_0^2/\left(4\pi\lambda_{ab}\right)^2$ [24]. In our case the anisotropy factor $\gamma \approx 150$ is comparable with the ratio $\lambda_{ab}/s$ and the magnetic coupling between pancake vortices in neighboring layers may influence the melting transition. We calculated the shift of the melting transition caused by magnetic coupling using perturbation theory and obtain

$$T_m\left(B\right) \approx 0.13(\varepsilon_0 a/\gamma)(1 + 0.23a^2/\lambda_{ab}^2). \quad (3)$$

The position of both the *estimated* $T_m$ (closed arrows) and *experimentally determined* $T_g$ (open arrows) is indicated in Fig. 5. We find that the glass transition fields exceed the calculated melting fields in a clean material by ∼15−20%, while the irreversibility fields are even smaller in a single crystal. It is generally true that irreversibility is resolution limited and lies lower than $T_m$. It has been established that *point* disorder drives the glass transition *below* the melting line [6], while *correlated* disorder drives it *above* the melting line [25]. Therefore, our results suggest that pinning in our films is dominated by correlated disorder, presumably dislocations [26]. This is in contrast to single crystals where point disorder is likely to dominate. In our films, at glass temperatures in the isolated vortex regime in the solid phase, $B_w$ decreases about two times in comparison with low temperatures and $r_w$ increases to 35 nm at 80 K. The field dependence is completely smooth near the glass transition. These results strongly imply that vortex lines are preserved across the glass transition for $T \geq 70$ K.

In conclusion, we have measured the JPR in Tl-2212 thin films using THz-TDS in transmission. We used the JPR frequency measurements as a probe to study the interlayer phase coherence as a function of temperature and magnetic fields above and below the melting line. Our results show that in Tl-2212 films the glass transition takes place probably due to disorder inherent to the films. Vortex lines exist in the liquid state in magnetic fields below 2.5 kG. We conclude that Tl-2212 films, at least in the low magnetic field portion of the phase diagram, behave as Y-123, and not as Bi-2212 single crystals despite the closer anisotropy ratios of Bi-2212 and Tl-2212.

We thank Superconductivity Technologies for providing the Tl-2212 films. This research was supported by the UC Campus-Laboratory Collaborations and by the Los Alamos LDRD Program by the U.S. DOE. Work in Argonne was supported by the U.S. DOE, Office of Science, under contract No. W-31-109-ENG-38.

---

[1] G. Blatter *et al.*, Rev. Mod. Phys. **66**, 1125 (1994).
[2] E. Zeldov *et al.*, Nature (London) **375**, 373 (1995).
[3] A. Schilling *et al.*, Nature (London) **382**, 791 (1996).
[4] B. Khaykovich *et al.*, Phys. Rev. Lett. **76**, 2555 (1996).
[5] H. Safar *et al.*, Phys. Rev. Lett. **72**, 1272 (1994); Yu. Eltsev and Ö. Rapp, ibid. **75**, 2446 (1995); A. Pautrat *et al.*, Phys. Rev. B, **59**, 199 (1999)
[6] L.M. Paulius *et al.*, Phys. Rev. B **61**, R11910 (2000).
[7] J. R. Clem, Phys. Rev. B **43**, 7837 (1991).
[8] T. Shibauchi *et al.*, Phys. Rev. Lett. **83**, 1010 (1999).
[9] M. B. Gaifullin *et al.*, Phys. Rev. Lett. **84**, 2945 (2000).
[10] A. E. Koshelev, L. N. Bulaevskii, and M. P. Maley, Phys. Rev. B **62**, 14403 (2000).
[11] V. K. Thorsmølle *et al.*, Opt. Lett. **26**, 1292 (2001).
[12] M. B. Gaifullin *et al.*, Phys. Rev. Lett. **83**, 3928 (1999).
[13] L. N. Bulaevskii *et al.*, Phys. Rev. B **61**, R3819 (2000).
[14] A. A. Tsvetkov *et al.*, Proc. SPIE **3480**, 2 (1998).
[15] R. D. Averitt *et al.*, J. Opt. Soc. Am. B **17**, 327 (2000).
[16] V. K. Thorsmølle, Ph.D. Thesis, UCLA (2001).
[17] A. E. Koshelev and L. N. Bulaevskii, Physica C **341-348**, 1503 (2000).
[18] A. Mazilu *et al.*, Phys. Rev. B **58**, R8909 (1998).
[19] R. H. Koch *et al.*, Phys. Rev. Lett. **63**, 1511 (1989).
[20] D. Dulić *et al.*, Phys. Rev. Lett. **86**, 4660 (2001).
[21] V. Hardy *et al.*, Phys. Rev. B **56**, 130 (1997).
[22] A. E. Koshelev *et al.*, Phys. Rev. B **53**, 2786 (1996).
[23] D. Dulić *et al.*, Phys. Rev. B **60**, R15051 (1999).
[24] A. E. Koshelev and H. Nordborg, Phys. Rev. B **59**, 4358 (1999).
[25] W. K. Kwok *et al.*, Phys. Rev. Lett. **84**, 3706 (2000).
[26] B. Dam *et al.*, Nature **399**, 439 (1999).